

Evidence against the polarization rotation model of piezoelectric perovskites at the morphotropic phase boundary

J. Frantti,* Y. Fujioka, and R. M. Nieminen

COMP/Department of Applied Physics, Helsinki University of Technology, FI-02015-HUT, Finland

(Dated: October 15, 2008)

The origin of the very large piezoelectric response observed in the vicinity of the morphotropic phase boundary (MPB) in perovskite lead zirconate titanate and related systems has been under intensive studies. Polarization rotation ideas are frequently invoked to explain the piezoelectric properties. It was recently reported that lead titanate undergoes a phase transformation sequence $P4mm \rightarrow Pm \rightarrow Cm \rightarrow R\bar{3}c$ at 10 K as a function of hydrostatic pressure [M. Ahart et al. Nature Letters. **451**, 545 (2008)]. We demonstrate that this interpretation is not correct by (i) simulating the reported diffraction patterns, and (ii) by density-functional theory computations which show that neither the Pm , Cm nor $Pmm2$ phase is stable in the studied pressure range, and further show that octahedral tilting is the key stabilization mechanism under high pressure. Notes on a more general ground are given to demonstrate that a continuous phase transition between rhombohedral and tetragonal phases via intermediate monoclinic phase is not possible. Thus, two-phase co-existence in the vicinity of the phase transition region is probable and has an important role for electromechanical properties.

The polarization rotation (PR) model [1, 2] has been proposed to explain the large electromechanical coupling coefficients observed in ferroelectric perovskites in the vicinity of the morphotropic phase boundary (MPB). The MPB region separates tetragonal and rhombohedral phases, which do not have a group-subgroup relationship and thus no continuous transition between the phases is possible. The most intensively studied systems are solid solutions, prime examples being lead zirconate titanate, $Pb(Zr_xTi_{1-x})O_3$, (PZT) and $xPb(Mg_{1/3}Nb_{2/3})O_3-(1-x)PbTiO_3$ (PMN-PT). The essential feature of the PR model is the insertion of one (or more) low-symmetry phase(s) to continuously (via group-subgroup chains) connect the tetragonal and rhombohedral phases separated by the MPB in order to continuously rotate the polarization vector by an electric field or pressure between the pseudo-cubic [001] and [111] directions along the $(\bar{1}\bar{1}0)$ plane. This rotation path was predicted to be accompanied by a large electromechanical response [3]. There are, however, several ambiguities related to the PR model (see, e.g., Ref. 4) and experimental studies interpreted in terms of this idea. As an example, the pressure induced phase transitions of lead titanate ($PbTiO_3$, PT) are considered below. Hydrostatic pressure induces similar structural changes as are observed to occur due to the substitution of Ti by a larger cation, such as Zr, causing so called “chemical pressure”.

At high temperatures PT undergoes a phase transition between the $P4mm$ and $Pm\bar{3}m$ phases [5]. At room temperature PT transforms to a cubic phase through a second-order transition at 12.1 GPa [6], whereas it was predicted through density-functional theory (DFT) computations that a phase transition between $P4mm$ and $R\bar{3}c$ phases occurs at 9 GPa at 0 K [7]. Notably the latter phase transition is similar to the phase transition observed in PZT as a function of Zr composition. In

simplest terms, one expects to have three different phase boundaries in the pressure-temperature plane of PT, separating the $P4mm$ and $Pm\bar{3}m$, $P4mm$ and $R\bar{3}c$ and $R\bar{3}c$ and $Pm\bar{3}m$ phases. A very different interpretation was recently given in Ref. 8, according to which the phase transition from the $P4mm$ to $R\bar{3}c$ phase would occur via monoclinic phases, which was further claimed to give support to the PR model. We demonstrate that (i) the single phase model is incorrect in the vicinity of the phase transition, (ii) the monoclinic distortions reported earlier are not stable, (iii) summarize the arguments which show that the phase transition must be of first order and (iv) outline the method for determining the piezoelectric properties in the vicinity of the phase boundary.

Computational methods. The DFT code ABINIT [9, 10] was used to compute the total energies and phonon frequencies and eigenvectors [11] at different pressures. The computations were carried out within the local-density approximation and a plane wave basis. Norm-conserving pseudopotentials were generated using the OPIUM package [12]. A more detailed description of the computational approach is available in Ref. 7. For the simulation of the X-ray diffraction patterns the Powder Cell program was used [13]. The lattice parameters were adapted from Ref. 8. The asymmetric unit was not given in Ref. 8, and thus the atomic positions were estimated using the values found from the DFT computations, which are close to the values estimated from our high-pressure neutron powder diffraction experiments at few GPa pressures [14].

Notes on the X-ray diffraction and Raman scattering analysis. According to Ref. 8, PT undergoes a phase transformation sequence $P4mm \rightarrow Pm \rightarrow Cm \rightarrow R\bar{3}c$ at 10 K as a function of hydrostatic pressure. We show that the X-ray diffraction (XRD) pattern collected at 13.2 GPa [8] is not consistent with the reported Pm sym-

metry by simulating the corresponding pattern. Fig. 1 shows that the reflection positions and intensities significantly deviate from the experimental ones and also from the fits (shown by black continuous lines). It is worth to note that in the case of PT the pseudo-cubic 110 reflections have the strongest XRD intensities. The 13.2 GPa XRD pattern shown in Fig. 1 more likely corresponds to a two-phase diffraction pattern. This is seen by studying the intensities of the 100 and 001 reflections: for tetragonal and pseudo-tetragonal structures the intensity ratio should roughly be 2:1 (as is seen from the diffraction pattern collected at 8.4 GPa, Fig. 1), whereas it is roughly 0.9:1 for the 13.2 GPa data.

It was stated that the Raman scattering data reflect the monoclinic M_C (Pm phase) to monoclinic M_A (Cm) and the monoclinic M_A to rhombohedral phase transitions [8]. We find this assignment questionable, since the phonon symmetries, central for the phase transition studies, were not addressed. For example, the B_1 -symmetry normal mode in the $P4mm$ phase breaks the fourfold symmetry [16], whereas the A_1 symmetry modes preserve it. The spectral features below 100 cm^{-1} include several peaks from the A_1 symmetry modes alone, due to the strong anharmonicity of the $A_1(1TO)$ mode [17, 18], in addition to the E -symmetry modes and Rayleigh scattering (which dominates the region close to the laser line, as was noted in Ref. 6). It was rather recently that the $A_1(1TO)$ mode was identified in PT [17, 18]: many earlier assignments dismissed this mode since the line shape was very asymmetric and turned out to be consisted of many subpeaks. In practice this means that, in the vicinity of the phase transition, it is hard to identify the number of modes at the low-frequency region, not to mention the difficulty of identifying their symmetries from the spectra collected without proper polarization measurements. This, in turn, prevents space group assignments.

DFT studies. DFT computations predict that PT undergoes a phase transition from the $P4mm$ phase to the $R3c$ phase at around 9 GPa [7]. In contrast, a phase transition sequence $P4mm \rightarrow Cm \rightarrow R3m \rightarrow Pm3m$ (phase transitions at 10, 12 and 22 GPa, respectively) was found in Ref. 19. The high-pressure end of this transition was more recently modified to form the sequence $R3m \rightarrow R3c \rightarrow R\bar{3}c \rightarrow R3c$ with phase transitions occurring at 18, 20 and 60 GPa, respectively [8]. In addition to the phases listed in Ref. 7, we carried out similar computations for the Pm and $Pmm2$ phases. For consistency, phonon frequencies of the $R3c$ phase were computed at 9, 10 and 15 GPa pressures at the Brillouin zone center and boundary points.

The main outcomes of our present and earlier computations are: (i) the $R3m$ phase is not stable (octahedral tilting makes $R3c$ phase favorable above 9 GPa), (ii) above 9 GPa tetragonal ($P4mm$ and $I4cm$), orthorhombic ($Cmm2$ and $Pmm2$) and monoclinic (Pm and Cm) phases were revealed to be unstable by the Brillouin

zone boundary modes and higher enthalpy values, (iii) no support for an intermediate phase was found, and (iv) no phonon instabilities were observed in the $R3c$ phase. In contrast, one of the Brillouin zone corner point $L = (\frac{\pi}{a}\frac{\pi}{a}\frac{\pi}{a})$ modes of the $R3m$ phase was unstable at 9 GPa pressure. The mode involved only oxygen displacements (this was the only mode which was found to be unstable: all modes at the (000) , $(00\frac{\pi}{a})$ and $(\frac{\pi}{a}\frac{\pi}{a}0)$ symmetry points were positive). The mode is depicted in Fig. 2. This corresponds to the mode where the upper and lower octahedra are tilted clockwise and anticlockwise about the threefold symmetry axis, thus again demonstrating that the octahedral tilting stabilizes the $R3c$ phase. This is due to the fact that octahedral tilting allows a more efficient compression [7, 20, 21].

We note that since the $R3m$ phase is not stable, it is somewhat hypothetical to consider the instability of an unstable phase. A more rigorous treatment, starting from the $P4mm$ phase, is given in Ref. 7, with the same outcome. Thus, the energetically favorable phase was obtained by allowing the crystal to relax according to the normal mode displacements of the unstable modes seen in the $P4mm$ phase. Thus the transition between $P4mm$ and $R3c$ phases is characterized by two-phase co-existence, in an analogous way to the phase transitions seen in PZT as a function of composition. This is an important prediction as it in turn suggests that the two-phase co-existence has a crucial role for the piezoelectric properties near the phase transition pressures in PT, in a similar way as was demonstrated in Ref. 22 for PZT in the vicinity of the MPB.

Symmetry considerations. Group-theoretical analysis indicates that, although the phase transition between monoclinic and tetragonal phases can be continuous, the transition between rhombohedral and monoclinic phases must be of first order [23]. Thus, even if one would have a monoclinic phase, it would not make the transformation path continuous. First-order transitions are often characterized by the two-phase co-existence, one phase being metastable over a finite temperature or pressure range. This is consistent with the experimentally known features of PZT according to which there is two-phase co-existence [21, 24, 25]. Neutron and X-ray powder diffraction studies revealed that the polarization vector in the monoclinic Cm phase is very close to the pseudo-cubic [001] direction, and hardly rotates from that direction [21, 25], in contrast to what one anticipates from the PR model. Thus the polarization vector changes discontinuously when the transition from the pseudo-tetragonal monoclinic to the rhombohedral phase occurs. As Li et al. noted, “the availability of multiple phases at the MPB makes it possible for the polarization to thread through the ceramic” [22].

How to model the piezoelectric response? The piezoelectric response can be divided to extrinsic and intrinsic contributions. The latter is due to the changes in

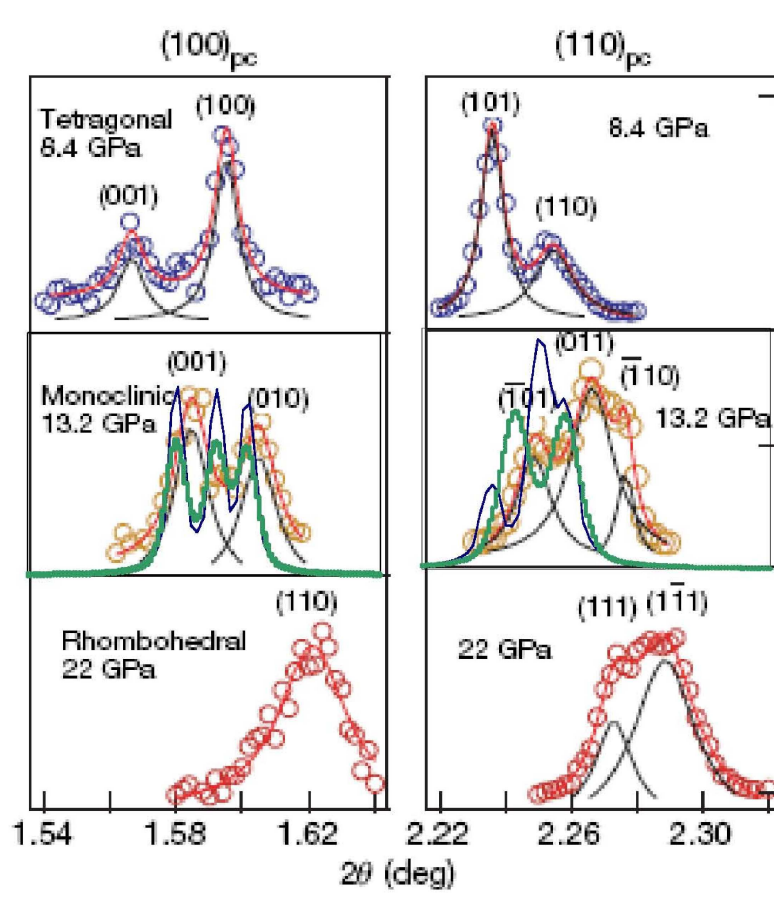


FIG. 1: X-ray diffraction data collected on PT at 10 K. The figure is adapted from Ref. 8. The green and blue lines (middle panels) were added by us. The green line shows the simulated Pm pattern using the lattice parameters given in Ref. 8. The model where the a and b axes are switched (blue line) does not improve the fit [15]. Neither of the one-phase Pm structure model fits the peak (black lines) positions and intensities (e.g., the reflection labelled as (110) is not modelled, and cannot be explained by preferred orientation).

electron densities as a response to an applied field or stress and can be computed through standard density-functional theory methods. The extrinsic part is significantly more challenging, as it involves domain wall motions and changes in the phase fractions in the vicinity of the phase-boundary (e.g., between tetragonal and rhombohedral phases). In the case of poled ceramics one first computes the necessary angular averages of the piezoelectric constants and takes their dependence on temperature, composition or stress into account. This dependence is notable in the vicinity of the phase transition. For intrinsic contribution such a computation is rather straightforward. However, the description of domain wall motion due to an applied electric field or stress for different composition or at different temperatures is nontrivial task.

In conclusion, evidence against the applicability of the polarization rotation model to perovskites is strong. Instead, the currently known best piezoelectric perovskites possess a so-called morphotropic phase boundary at which

a first-order phase transition between rhombohedral and tetragonal (or pseudo-tetragonal) phases takes place. For the electromechanical properties it is important to note that this transition exhibits two-phase co-existence. Structural factors responsible for the stabilization of the rhombohedral phase, either at large hydrostatic pressures or large chemical pressures (as occurs in $\text{Pb}(\text{Zr}_x\text{Ti}_{1-x})\text{O}_3$ with increasing x) were addressed.

Y. F. is grateful for the Finnish Cultural Foundation and Tekniikan Edistämissäätiö foundation for financial support. This project was supported by the Academy of Finland (Project Nos 207071 and 207501 and the Center of Excellence Program 2006-2011). Finnish IT Center for Science (CSC) is acknowledged for providing computing resources.

* johannes.frantti@hut.fi

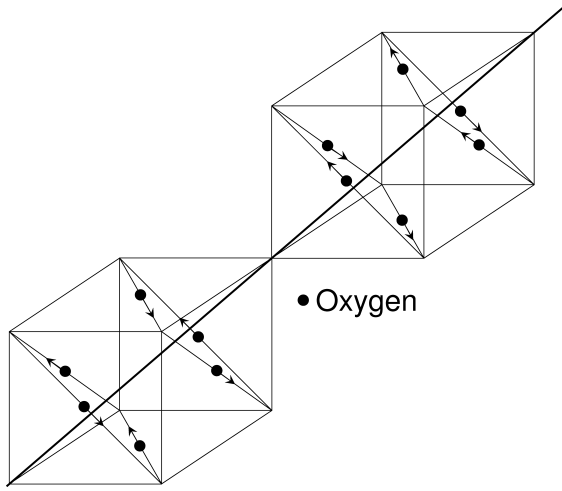


FIG. 2: . The unstable normal mode of the $R3m$ phase at the $L = (\frac{\pi}{a}, \frac{\pi}{a}, \frac{\pi}{a})$ point involves only oxygen ions. Two rhombohedral unit cells are shown: it is seen that the two octahedra are tilted about the threefold axes clockwise and anticlockwise. The condensation of this mode corresponds to the phase transition $R3m \rightarrow R3c$. All the modes had positive frequencies when the $R3c$ phase was used. The bold line is the threefold rotation axis.

- [1] H. Fu and R. E. Cohen, *Nature*. **403**, 281 (2000).
- [2] R. Guo, L. E. Cross, S.-E. Park, B. Noheda, D. E. Cox, and G. Shirane, *Phys. Rev. Lett.* **84**, 5423 (2000).
- [3] R. E. Cohen, *Nature*. **441**, 941 (2006).
- [4] E. H. Kisi and J. S. Forrester, *J. Phys. Condens. Matter*. **20**, 1 (2008).
- [5] A. Sani, M. Hanfland, and D. Levy, *J. Solid State Chem.* **167**, 446 (2002).
- [6] J. A. Sanjurjo, E. López-Cruz, and G. Burns, *Phys. Rev. B*. **28**, 7260 (1983).
- [7] J. Frantti, Y. Fujioka, and R. M. Nieminen, *J. Phys. Chem. B*. **111**, 4287 (2007).
- [8] M. Ahart, M. Somayazulu, R. E. Cohen, G. P. Dera, H. Mao, J. Russell, J. Hemley, Y. Ren, P. Liermann, and Z. Wu, *Nature* **451**, 545 (2008).
- [9] X. Gonze, J.-M. Beuken, R. Caracas, F. Detraux, M. Fuchs, G.-M. Rignanese, L. Sindic, M. Verstraete, G. Zerah, F. Jollet, et al., *Comput. Mater. Sci.* **25**, 478 (2002).
- [10] X. Gonze, G.-M. Rignanese, M. Verstraete, J.-M. Beuken, Y. Pouillon, R. Caracas, F. Jollet, M. Torrent, G. Zerah, M. Mikami, et al., *Zeit. Kristallogr.* **220**, 558 (2005).
- [11] X. Gonze, *Phys. Rev. B*. **55**, 10337 (1997).
- [12] A. M. Rappe, K. M. Rabe, E. Kaxiras, , and J. D. Joannopoulos, *Phys. Rev. B*. **41**, 1227 (1990).
- [13] W. Krans and G. Nolze (1996).
- [14] J. Frantti, Y. Fujioka, J. Zhang, S. Vogel, S. Wang, and R. M. Nieminen, Unpublished.
- [15] According to the authors of Ref. 8, a and b were inadvertently switched for Pm . Information obtained through Nature Editorial Office.
- [16] J. Frantti, J. Lappalainen, V. Lantto, S. Nishio, and M. Kakihana, *J. J. Appl. Phys.* **38**, 5679 (1999).
- [17] C. M. Foster, M. Grimsditch, Z. Li, and V. G. Karpov, *Phys. Rev. Lett.* **71**, 1258 (1993).
- [18] C. M. Foster, Z. Li, M. Grimsditch, S.-K. Chan, and D. J. Lam, *Phys. Rev. B*. **48**, 10160 (1993).
- [19] Z. Wu and R. E. Cohen, *Phys. Rev. Lett.* **95**, 037601 (2005).
- [20] N. W. Thomas and A. Beitollahi, *Acta Cryst. B*. **50**, 549 (1994).
- [21] J. Frantti, S. Ivanov, S. Eriksson, H. Rundlöf, V. Lantto, J. Lappalainen, and M. Kakihana, *Phys. Rev. B*. **66**, 064108 (2002).
- [22] J. Y. Li, R. C. Rogan, E. Üstündag, and K. Bhat-tacharya, *Nature Mat.* **776**, 4 (2005).
- [23] I. A. Sergienko, Y. M. Gufan, and S. Urazhdin, *Phys. Rev. B*. **65**, 144104 (2002).
- [24] D. E. Cox, B. Noheda, and G. Shirane, *Phys. Rev. B*. **71**, 134110 (2005).
- [25] J. Frantti, S. Eriksson, S. Hull, V. Lantto, H. Rundlöf, and M. Kakihana, *J. Phys. Condens. Matter*. **15**, 6031 (2003).